

A Brief Literature Review of the Available Atom Probe Tomography Datasets for Irradiated Stainless Steels

3002008926

A Brief Literature Review of the Available Atom Probe Tomography Datasets for Irradiated Stainless Steels

3002008926

Technical Update, October 2016

EPRI Project Manager

P. Chou

All or a portion of the requirements of the EPRI Nuclear Quality Assurance Program apply to this product.

YES



DISCLAIMER OF WARRANTIES AND LIMITATION OF LIABILITIES

THIS DOCUMENT WAS PREPARED BY THE ORGANIZATION(S) NAMED BELOW AS AN ACCOUNT OF WORK SPONSORED OR COSPONSORED BY THE ELECTRIC POWER RESEARCH INSTITUTE, INC. (EPRI). NEITHER EPRI, ANY MEMBER OF EPRI, ANY COSPONSOR, THE ORGANIZATION(S) BELOW, NOR ANY PERSON ACTING ON BEHALF OF ANY OF THEM:

(A) MAKES ANY WARRANTY OR REPRESENTATION WHATSOEVER, EXPRESS OR IMPLIED, (I) WITH RESPECT TO THE USE OF ANY INFORMATION, APPARATUS, METHOD, PROCESS, OR SIMILAR ITEM DISCLOSED IN THIS DOCUMENT, INCLUDING MERCHANTABILITY AND FITNESS FOR A PARTICULAR PURPOSE, OR (II) THAT SUCH USE DOES NOT INFRINGE ON OR INTERFERE WITH PRIVATELY OWNED RIGHTS, INCLUDING ANY PARTY'S INTELLECTUAL PROPERTY, OR (III) THAT THIS DOCUMENT IS SUITABLE TO ANY PARTICULAR USER'S CIRCUMSTANCE; OR

(B) ASSUMES RESPONSIBILITY FOR ANY DAMAGES OR OTHER LIABILITY WHATSOEVER (INCLUDING ANY CONSEQUENTIAL DAMAGES, EVEN IF EPRI OR ANY EPRI REPRESENTATIVE HAS BEEN ADVISED OF THE POSSIBILITY OF SUCH DAMAGES) RESULTING FROM YOUR SELECTION OR USE OF THIS DOCUMENT OR ANY INFORMATION, APPARATUS, METHOD, PROCESS, OR SIMILAR ITEM DISCLOSED IN THIS DOCUMENT.

REFERENCE HEREIN TO ANY SPECIFIC COMMERCIAL PRODUCT, PROCESS, OR SERVICE BY ITS TRADE NAME, TRADEMARK, MANUFACTURER, OR OTHERWISE, DOES NOT NECESSARILY CONSTITUTE OR IMPLY ITS ENDORSEMENT, RECOMMENDATION, OR FAVORING BY EPRI.

THE ELECTRIC POWER RESEARCH INSTITUTE (EPRI) PREPARED THIS REPORT.

THE TECHNICAL CONTENTS OF THIS PRODUCT WERE **NOT** PREPARED IN ACCORDANCE WITH THE EPRI QUALITY PROGRAM MANUAL THAT FULFILLS THE REQUIREMENTS OF 10 CFR 50, APPENDIX B. THIS PRODUCT IS **NOT** SUBJECT TO THE REQUIREMENTS OF 10 CFR PART 21.

This is an EPRI Technical Update report. A Technical Update report is intended as an informal report of continuing research, a meeting, or a topical study. It is not a final EPRI technical report.

NOTE

For further information about EPRI, call the EPRI Customer Assistance Center at 800.313.3774 or e-mail askepri@epri.com.

Electric Power Research Institute, EPRI, and TOGETHER...SHAPING THE FUTURE OF ELECTRICITY are registered service marks of the Electric Power Research Institute, Inc.

Copyright © 2016 Electric Power Research Institute, Inc. All rights reserved.

ACKNOWLEDGMENTS

The Electric Power Research Institute (EPRI) prepared this report.

Principal Investigator

P. Chou

This report describes research sponsored by EPRI.

This publication is a corporate document that should be cited in the literature in the following manner:

A Brief Literature Review of the Available Atom Probe Tomography Datasets for Irradiated Stainless Steels. EPRI, Palo Alto, CA: 2016. 3002008926.

ABSTRACT

A number of studies in the literature have concluded that dislocation loops, irradiation-induced hardening, and radiation-induced segregation at the grain boundary are not sufficient indices to assess susceptibility to irradiation assisted stress corrosion cracking (IASCC). Irradiation induced hardening and dislocation loop density and size, as determined by transmission electron microscopy (TEM), no longer change significantly past 5 dpa. However, studies of IASCC crack initiation of field-retrieved materials suggest fluence is an important factor up to 20-25 dpa. It is therefore not possible to diagnose relative degrees of IASCC susceptibility based on these parameters. This update reviews the data in EPRI's *Program on Technology Innovation: Effects of Post Irradiation Annealing on IASCC* (3002005475) along with other studies that apply TEM to quantify radiation-induced dislocation loops *and* atom probe tomography to quantify radiation-induced solute clusters.

The aggregate data suggest that proton-irradiated and light water reactor (LWR)-neutron-irradiated stainless steels have different values of the following ratio: solute cluster number density/Frank loop number density. The data also suggest that the ratio continues to increase beyond 5 dpa when the Frank loop number density and size saturate, driven by the increase in solute cluster number density. It is therefore important to investigate and establish whether clusters affect irradiated materials behavior, particularly past 5 dpa. If they do, then changes in solute cluster number density, size, volume fraction, or cluster/Frank loop ratio may serve as an index of susceptibility that can guide IASCC risk assessment.

Keywords

Atom probe tomography
Irradiated stainless steel
Irradiated microstructure
Solute clusters
Frank loops
Irradiation assisted stress corrosion cracking (IASCC)

CONTENTS

ABSTRACT	v
1 REVIEW OF AVAILABLE DATA IN THE LITERATURE	1-1
2 REFERENCES	2-1

LIST OF FIGURES

- Figure 1-1 The ratio of (cluster number density/Frank loop number density) has been plotted versus dose. These datasets have been analyzed according to the same protocol. The datapoint in green (proton-irradiated 304SS) comes from EPRI 3002005475. The datapoints in blue [(BWR) neutron-irradiated 304L SS] comes from the CRIEPI-EPRI-UMich study [7]. Note that the proton-irradiated dose of 10 dpa “full-cascade” has been divided by 2 to convert it to 5 dpa “Khinchin-Pease” to facilitate comparison to (BWR) neutron-irradiated data [9]. Only Ni/Si clusters have been plotted because the CRIEPI-EPRI-UMich study indicate that they are strongly associated with dislocation loops, whereas Al-enriched clusters and Cu-enriched clusters are not.1-2
- Figure 1-2 The ratio of (cluster number density/Frank loop number density) plotted versus dose, including four data points not in Figure 1-1, whose APT data not analyzed by the same protocol. Two additional data points from proton-irradiated stainless steels, at 2.5 dpa came from [3, 5]; one additional data point from PWR-irradiated 304SS came from [4]; and one additional data from PWR-irradiated CW 316SS came from [8]. For proton irradiation, “full-cascade” dose values calculated by SRIM has been divided by 2 to convert them to “Khinchin-Pease” dose values to facilitate comparison to neutron-irradiated data [9]. Only Ni/Si clusters have been plotted because the CRIEPI-EPRI-UMich study [7] indicate that they are strongly associated with dislocation loops, whereas Al-enriched clusters and Cu-enriched clusters are not.1-4

1

REVIEW OF AVAILABLE DATA IN THE LITERATURE

Several studies in the literature, including the work documented in *Program on Technology Innovation: Effects of Post Irradiation Annealing on IASCC*. EPRI, Palo Alto, CA: 2015. 3002005475, have now applied transmission electron microscopy (TEM) to quantify dislocation loops and atom probe tomography (APT) to quantify solute clusters [1, 3, 4, 6, 7] in the irradiated microstructure of stainless steels. It is of interest to review, in this brief update, the observations and the reported cluster/loop ratios, which also touch upon differences that may exist between proton-irradiated and LWR-irradiated microstructures.

Currently, different researchers can apply different parameters to quantify APT data within the IVAS analysis software provided by the manufacturer, Cameca¹, and a few groups use proprietary algorithms. Therefore, data from different researchers cannot be simply collected together and analyzed, except with caution and caveats. For this reason, EPRI and EDF have sponsored an APT Round Robin, involving 10 international organizations, to achieve better agreement on how APT data should be collected and analyzed; one of the co-PI's of EPRI 3002005475, Emmanuelle Marquis, is the technical advisor to the Round Robin, and the other co-PIs are participants.

However, several BWR-irradiated stainless steels in the range of 3.5-13 dpa have been analyzed by Marquis and coworkers [7], according to the same protocol as this study² [6]. Therefore, these data (both neutron-irradiated and proton-irradiated) can be considered together with assurance and are plotted in Figure 1-1. Only Ni-Si clusters are considered because they are strongly associated with dislocation loops, whereas Al-enriched clusters and Cu-enriched clusters are not [7]. Their number densities are compared to the Frank loop number densities via a ratio.

The (BWR) neutron-irradiated cluster/loop ratio vary from 0.1 at 3.5 dpa to 1.7 at 13 dpa. APT analysis indicates that Ni-Si-rich clusters are observed primarily on Si-segregated dislocation loops and fragments [7]. This is not surprising, since dislocation loops can serve as sites of heterogeneous nucleation.

In contrast, the proton-irradiated CP304 of EPRI 3002005475 has a much higher cluster/loop ratio of 14.6, suggesting that a substantial number of “free clusters” is present. The linear density of Ni-Si rich clusters on dislocations, as determined by APT, is 12 clusters per 100 nm. The average dislocation loop diameter according to APT is 9.4 nm (Table 3-4 of EPRI 3002005475) [or 7.4 nm according to TEM (Table 3-3 of EPRI 3002005475)]. Therefore, there are ~3.5 clusters are associated with the average dislocation loop. Consequently, approximately $(3.5/14.6) \times 100\% = 24\%$ of the clusters are associated with dislocation loops while the majority ~76% should be “free clusters.”

¹ Cameca became the only manufacturer of atom probe tomographs, after its acquisition of Imago in 2010.

² The raw APT datasets were collected by CRIEPI (Japan) within a CRIEPI-EPRI collaboration using voltage-only mode (no laser assist), as are the data of this study.

(Ni-Si Cluster # Density/Frank Loop # Density) vs. Dose

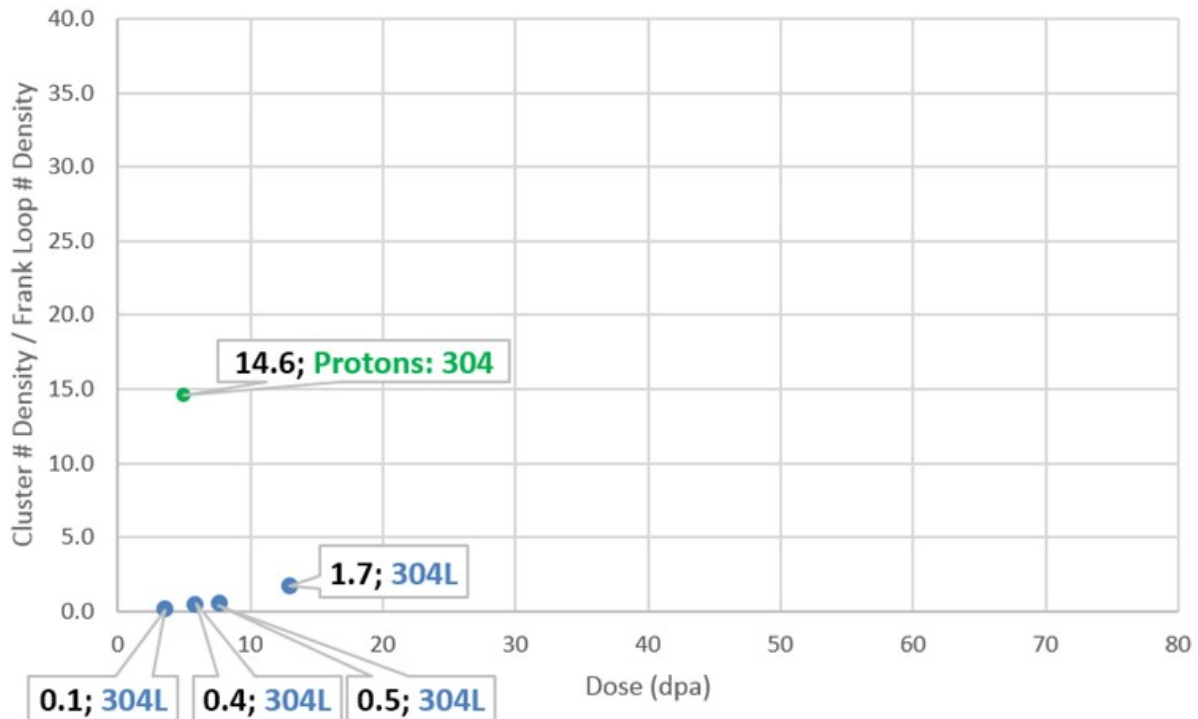


Figure 1-1

The ratio of (cluster number density/Frank loop number density) has been plotted versus dose. These datasets have been analyzed according to the same protocol. The datapoint in green (proton-irradiated 304SS) comes from EPRI 3002005475. The datapoints in blue [(BWR) neutron-irradiated 304L SS] comes from the CRIEPI-EPRI-UMich study [7]. Note that the proton-irradiated dose of 10 dpa “full-cascade” has been divided by 2 to convert it to 5 dpa “Khinchin-Pease” to facilitate comparison to (BWR) neutron-irradiated data [9]. Only Ni/Si clusters have been plotted because the CRIEPI-EPRI-UMich study indicate that they are strongly associated with dislocation loops, whereas Al-enriched clusters and Cu-enriched clusters are not.

The existence of “free clusters” might be somewhat puzzling, since homogeneous nucleation is difficult. One possible explanation is that as cluster decoration of dislocation loops progress past, say, 4 clusters, the dislocation loops are consumed and becomes a larger cluster. Dislocation loop density saturates around 2 dpa and their size saturate around 5 dpa. [10] Clusters might therefore have a role in maintaining the steady-state dislocation loop density, balancing their creation and annihilation.

Four additional data points are added to the same plot in Figure 1-2. *The APT data analysis was conducted according to different protocols, so they must be considered with caution and, at most, we can only interpret trends.* But it is interesting to note that:

- The two additional proton-irradiated data points [3, 5] also indicate high cluster/loop ratios relative to neutron-irradiated data points at comparable dose.

- The (PWR) neutron-irradiated data point at 24 dpa (cluster/loop ratio of 6.9) [4], when considered together with the BWR neutron-irradiated data points, suggests that the cluster/loop ratio can continue to increase with dose. Since dislocation loop density saturates at relatively low doses (although there is scatter) [10], the increase in the cluster/loop ratio is driven by the increase in the cluster number density.
- The (PWR) neutron-irradiated data point from CW 316SS at 74 dpa (cluster/loop ratio of 38.5) [8], may suggest that the cluster/loop ratio can continue to increase with dose, but may also suggest that network dislocations associated with cold work act as nucleation sites that enhance the formation of solute clusters.³ In this context, it should be noted that there is only one data point from CW 316SS in Figure 1-2. More data is clearly necessary.

Although Figure 1-2 can be interpreted to suggest that the cluster/loop ratio can continue to increase with dose, the increase cannot, of course, persist indefinitely, since Si is the “limiting reactant” and will run out earlier or later, depending on the amount of Si from heat to heat. For example, in their study, Jiao and Was [3, 5] indicated that at 4.5% volume fraction of Ni-Si clusters, 19-34% of the available Si in their material were consumed by Ni-Si clusters. (The data points from their study are included in Figure 1-2.)

Broader assessment of the details discussed here requires more consistent, accurate quantification among different studies.

The reason such questions are of practical interest is that dislocation loop density and size generally saturates (no longer changes significantly) past ~5 dpa [10], but studies of IASCC crack initiation of field-retrieved materials suggest fluence is an important factor up to 20-25 dpa. Therefore, it has not been possible to “diagnose” relative degrees of IASCC susceptibility based on past microstructural examinations that focused on TEM quantification of dislocation loops.

It is therefore important to investigate and establish whether clusters affect irradiated materials behavior, particularly past 5 dpa. If they do, then changes in cluster number density, size, volume fraction, or cluster/loop ratio may serve as an index of susceptibility that can guide IASCC risk assessment.

³ The network dislocations associated with cold-worked stainless steels are typically removed by ~20 dpa under neutron irradiation, but prior to their disappearance, they may influence the formation of solute clusters.

(Ni-Si Cluster # Density/Frank Loop # Density) vs. Dose

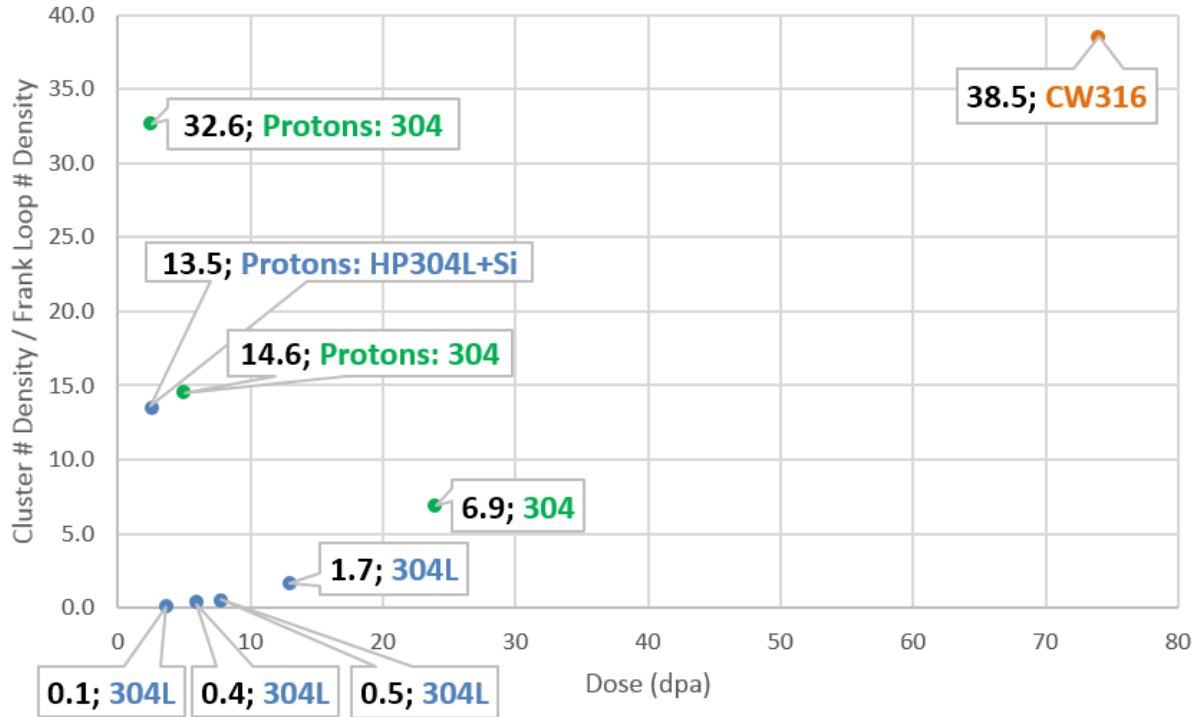


Figure 1-2
 The ratio of (cluster number density/Frank loop number density) plotted versus dose, including four data points not in Figure 1-1, whose APT data not analyzed by the same protocol. Two additional data points from proton-irradiated stainless steels, at 2.5 dpa came from [3, 5]; one additional data point from PWR-irradiated 304SS came from [4]; and one additional data from PWR-irradiated CW 316SS came from [8]. For proton irradiation, “full-cascade” dose values calculated by SRIM has been divided by 2 to convert them to “Khinchin-Pease” dose values to facilitate comparison to neutron-irradiated data [9]. Only Ni/Si clusters have been plotted because the CRIEPI-EPRI-UMich study [7] indicate that they are strongly associated with dislocation loops, whereas Al-enriched clusters and Cu-enriched clusters are not.

2

REFERENCES

1. Etienne, Radiguet, Pareige, Massoud, Pokor, J Nuclear Materials 382 (2008) 64-69.
2. *BWRVIP-221: BWR Vessel and Internals Project, Crack Growth in High Fluence BWR Materials – Phase1: Crack Growth Rate Testing of Types 304L and 316L at Doses Ranging from 3.5 to 13 dpa.* EPRI, Palo Alto, CA: 2009. 1019079.
3. *Potential for Atom Probe Tomography in Understanding Irradiation Assisted Stress Corrosion Cracking: Characterization of Proton-Irradiated, Si-Containing Stainless Steels.* EPRI, Palo Alto, CA: 2011. 1022815.
4. Toyama, Nozawa, Van Renterghem, Matsukawa, Hatakeyama, Nagai, Al Mazouzi, Van Dyck, J of Nuclear Materials 418 (2011) 62-68.
5. Jiao and Was, Acta Materialia 59 (2011) 122-1238.
6. Chen, Chou, Marquis, J. Nuclear Materials 451 (2014) 130-136.
7. Chou, Soneda, Nishida, Dohi, Marquis, Chen, Proceedings of Fontevraud 8 Conference: Contribution of Materials Investigations and Operating Experience to LWR's Safety, Performance and Reliability, September 15-18 2014, Avignon, France.
8. Fujii, Fukuya, J Nuclear Materials 469 (2016) 82-88.
9. R.E. Stoller, M.B. Toloczko, G.S. Was, A.G. Certain, S. Dwaraknath, F.A. Garner, Nuclear Instruments and Methods in Physics Research B 310 (2013) 75–80.
10. S. M. Bruemmer. E. P. Simonen, P. M. Scott, P. L. Andresen, G. S. Was, J. L. Nelson, Journal of Nuclear Materials, 274 (1999) 299-314.

Export Control Restrictions

Access to and use of EPRI Intellectual Property is granted with the specific understanding and requirement that responsibility for ensuring full compliance with all applicable U.S. and foreign export laws and regulations is being undertaken by you and your company. This includes an obligation to ensure that any individual receiving access hereunder who is not a U.S. citizen or permanent U.S. resident is permitted access under applicable U.S. and foreign export laws and regulations. In the event you are uncertain whether you or your company may lawfully obtain access to this EPRI Intellectual Property, you acknowledge that it is your obligation to consult with your company's legal counsel to determine whether this access is lawful. Although EPRI may make available on a case-by-case basis an informal assessment of the applicable U.S. export classification for specific EPRI Intellectual Property, you and your company acknowledge that this assessment is solely for informational purposes and not for reliance purposes. You and your company acknowledge that it is still the obligation of you and your company to make your own assessment of the applicable U.S. export classification and ensure compliance accordingly. You and your company understand and acknowledge your obligations to make a prompt report to EPRI and the appropriate authorities regarding any access to or use of EPRI Intellectual Property hereunder that may be in violation of applicable U.S. or foreign export laws or regulations.

The Electric Power Research Institute, Inc. (EPRI, www.epri.com) conducts research and development relating to the generation, delivery and use of electricity for the benefit of the public. An independent, nonprofit organization, EPRI brings together its scientists and engineers as well as experts from academia and industry to help address challenges in electricity, including reliability, efficiency, affordability, health, safety and the environment. EPRI members represent 90% of the electric utility revenue in the United States with international participation in 35 countries. EPRI's principal offices and laboratories are located in Palo Alto, Calif.; Charlotte, N.C.; Knoxville, Tenn.; and Lenox, Mass.

Together...Shaping the Future of Electricity